## Copper(II) sorption with tetrazolated Nitron D-5 polyacrylonitrile fibre

Y. V. Grigoriev, I. M. Grigorieva, S. V. Voitekhovich, O. A. Ivashkevich Research Institute for Physical Chemical Problems, Belarusian State University, Minsk, Belarus, e-mail: azole@bsu.by

Due to coordination ability polymers containing tetrazole derivatives are attractive as a sorbents for isolation of heavy metals from aqueous solutions [1–4]. In continuation of our investigations in the field of synthesis and chemistry of tetrazole derivatives [5] in the present work we studied the possibility of isolation of Cu<sup>2+</sup> from aqueous solutions using films of polymers prepared by azidation of the commercial Nitron D-5 polyacrylonitrile fibre. Tetrazolation of the initial fibre was carried out using NaN<sub>3</sub>/NH<sub>4</sub>Cl as azidation agent in dimethylformamide at 100 °C. Obtained polymers present copolymers of 5-vinyltetrazole, acrylonitrile, methyl acrylate and 2-acrylamido-2-methylpropanesulfonic acid.

$$\begin{bmatrix} H_2 & H \\ C & C & C \\ HN & N \end{bmatrix}_n \begin{bmatrix} H_2 & H \\ C & C \\ C & C \\ HN & N \end{bmatrix}_m \begin{bmatrix} H_2 & H \\ C & C \\ C & C$$

The content of tetrazolyl moieties varied from ~10 to ~90 % was adjusted by changing the azidation agent : initial polymer ratio.

Films of polymers investigated was found to sorb  $Cu^{2+}$  from dilute solutions of  $Cu(NO_3)_2$ . The degree of sorption increased with increasing of tetrazolation ratio (Fig), that indicated a key role of tetrazolyl moiety in the interaction of  $Cu^{2+}$  with a sorbent. The adsorbed  $Cu^{2+}$  ions were shown to be quantitatively removed from polymer formed by treatment with 0.1 M HCl. Sorbent regenerated were suitable for the further extraction of metal ions.

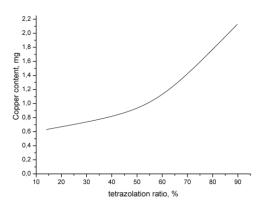


Fig. Dependence of sorbed  $Cu^{2+}$  amount vs tetrazolation ratio of sorbent (sorbent – 100 mg,  $2.7 \cdot 10^{-4}$  M  $Cu(NO_3)_2$ , 24 h, 20 °C).

## References

- 1. M.H. M. Alho, D. Grassi, A. Fernandez Girelli et al. *Environment. Chem. Lett.* (2009): 271.
- 2. S. Yan, M. Zhao, G. Lei et al. Appl. Polym. Sci. (2012): 382.
- 3. V.A. Kruglova, L.P. Shaulina, V.N. Kizhnyaev et al. Rus. J. Appl. Chem. (2011): 497.
- 4. A.V. Irgunova, N.V. Sirotinkin, M.V. Uspenskaja. Rus. J. Appl. Chem. (2001): 818.
- 5. Y.V. Grigoriev, S.V. Voitekhovich, P.N. Gaponik, O.A. Ivashkevich. *Sviridov Redings* (2014) 10: 193.